

The British University in Egypt

**BUE Scholar**

---

Chemical Engineering

Engineering

---

Fall 1-5-2019

## Optimization of the Catalytic Performance of Pd/Fe<sub>3</sub>O<sub>4</sub> Nanoparticles Prepared Via Microwave-Assisted Synthesis for Pharmaceutical and Catalysis Applications

Hany A. Elazab Dr

*The British University in Egypt*, hany.elazab@bue.edu.eg

Follow this and additional works at: [https://buescholar.bue.edu.eg/chem\\_eng](https://buescholar.bue.edu.eg/chem_eng)

 Part of the [Chemical Engineering Commons](#)

---

### Recommended Citation

Elazab, Hany A. Dr, "Optimization of the Catalytic Performance of Pd/Fe<sub>3</sub>O<sub>4</sub> Nanoparticles Prepared Via Microwave-Assisted Synthesis for Pharmaceutical and Catalysis Applications" (2019). *Chemical Engineering*. 103.

[https://buescholar.bue.edu.eg/chem\\_eng/103](https://buescholar.bue.edu.eg/chem_eng/103)

This Article is brought to you for free and open access by the Engineering at BUE Scholar. It has been accepted for inclusion in Chemical Engineering by an authorized administrator of BUE Scholar. For more information, please contact [bue.scholar@gmail.com](mailto:bue.scholar@gmail.com).

## Optimization of the catalytic performance of Pd/Fe<sub>3</sub>O<sub>4</sub> nanoparticles prepared via microwave-assisted synthesis for pharmaceutical and catalysis applications

Hany A. Elazab<sup>1,\*</sup>, Tamer T. El-Idreesy<sup>2,3</sup>

<sup>1</sup>Department of Chemical Engineering, Faculty of Engineering, The British University in Egypt, Cairo, Egypt.

<sup>2</sup>Department of Chemistry, Faculty of Science, Cairo University, Giza 12613, Egypt.

<sup>3</sup>Department of Chemistry, School of Sciences and Engineering, The American University in Cairo, New Cairo 11835, Egypt.

\*corresponding author e-mail address: [elazabha@vcu.edu](mailto:elazabha@vcu.edu)

### ABSTRACT

Microwave assisted synthesis technique was used to prepare palladium supported on iron oxide nanoparticles. The advantage of using microwave irradiation as a synthetic tool is due to its unique features as a one step, simple, versatile, and rapid process. The reactants are added simply at room temperature without using high-temperature injection. Hydrazine hydrate was added by the following ratios (0.1, 0.2, 0.3, 0.4, 0.6, 0.8, 1, 1.6, and 3) ml to the different prepared samples at room temperature in order to investigate its effect on the catalytic performance of the prepared catalysts. The prepared catalyst could be used as an ideal candidate not only for Pharmaceutical industry through cross-coupling reactions but also for low temperature oxidation catalysis of carbon monoxide and pharmaceutical applications as well. The experimental results showed that Pd/Fe<sub>3</sub>O<sub>4</sub> catalyst has a remarkable catalytic activity for carbon monoxide oxidation catalysis due to the strong interaction between palladium and iron oxide nanoparticles. This may be due to the small particle size (7-14 nm) and concentration ratio of the Pd nanoparticles dispersed on the surface of magnetite (Fe<sub>3</sub>O<sub>4</sub>). Those nanoparticles were characterized by various spectroscopic techniques including; X-ray photoelectron spectroscopy (XPS), X-ray diffraction (XRD), Vibrating Sample Magnetometer (VSM) and transmission electron microscopy (TEM).

**Keywords:** Microwave-assisted Synthesis, Pd nanoparticles, Magnetite nanoparticles, CO catalytic oxidation catalysis.

### 1. INTRODUCTION

Magnetic nanoparticles have vital importance as an attractive class of nanostructured materials according to its unique properties.[1-4] Nanostructured materials are of vital importance not only in industrial catalysis, but also in other research disciplines including advanced technological and medical applications, green chemistry, biology, and material science.[5-17]

Metal oxides play an important role as an ideal support in the field of heterogeneous catalysis in several applications not only including the production of chemicals, hydrocarbons, pharmaceuticals but also including removal of harmful volatile organic compounds and gases in order to minimize the environmental pollution.[9-15,18,19] Metal oxides are capable of providing an easy approach to disperse the particles at the nanoscale on its surface and hence, make it possible to avoid the potential agglomeration and sintering that could happen during the reactions.[5-15] Moreover, metal oxides play an important role via influencing the mechanism of the catalytic oxidation through the metal-metal oxide interface where electron transfer processes can take place.[9,20-23]

The oxidation catalysis of carbon monoxide has significant importance in pollution control due to its severe side effects and other serious symptoms that could lead to death even if under exposure to small amounts (ppm) as it is odorless and invisible gas.[24-27] Fe<sub>3</sub>O<sub>4</sub> nanoparticles are used as ideal catalyst supports due to its good chemical stability, low toxicity, and magnetic

properties.[9,10,13,15,18] The magnetic catalysts are considered among ideal catalysts that could achieve easy adoption of green chemical synthetic routes due to its easy recovery via applying a strong external magnetic field. [15] Transition metals including Pd, Pt and Rd nanoparticles are considered as the main active catalysts that transform carbon monoxide into carbon dioxide. The type of support, metal precursor, preparation and pre-treatment conditions, and catalytic reaction conditions are essential factors that directly affect the performance of a heterogeneous catalyst for CO oxidation through its impact on activity, selectivity and stability.[28-33]

The catalyst support nature is a decisive factor that could lead to the tendency of carbon monoxide molecules to be adsorbed on the catalyst surface. Hence, this will have a direct impact on the turnover that basically depends on the presence of surface sites that are open for O<sub>2</sub> adsorption and dissociation. Fe<sub>3</sub>O<sub>4</sub> nanoparticles act as ideal catalyst support for CO oxidation due to the presence of the Fe<sup>2+</sup> ion in Fe<sub>3</sub>O<sub>4</sub> that provides some reducible oxide characters. [34]

In this scientific research, we have made an enhancement to our previous research findings by using different ratios of hydrazine hydrate (0.1, 0.2, 0.3, 0.4, 0.6, 0.8, 1, 1.6, and 3) ml in order to investigate its effect on the catalytic performance of the prepared catalysts.


### 2. MATERIALS AND METHODS

**2.1. Chemicals.** All purchased chemicals were used without any other purification. Palladium nitrate, Fe (NO<sub>3</sub>)<sub>3</sub>.9H<sub>2</sub>O, and

hydrazine hydrate (80%, Hydrazine 51%) were purchased from Sigma Aldrich. For experimental synthesis described here, a

# Optimization of the catalytic performance of Pd/Fe<sub>3</sub>O<sub>4</sub> nanoparticles prepared via microwave-assisted synthesis for pharmaceutical and catalysis applications

microwave oven (2.45 GHz) operating at 600 – 1000 W was used in experimental procedure.

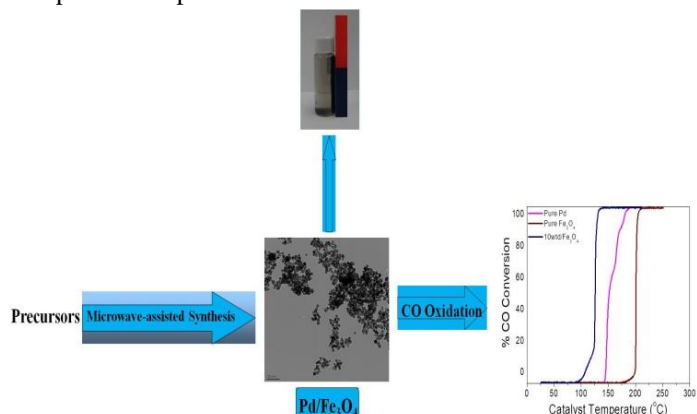

**Figure 1.** Graphical Abstract of Synthesis of Pd nanoparticles Supported on iron oxide

**2.2. Microwave-assisted Synthesis of Pd/Fe<sub>3</sub>O<sub>4</sub>.** In the experimental procedure of Pd/Fe<sub>3</sub>O<sub>4</sub> synthesis, different samples of a fixed ratio have been prepared with the ratio 20 wt % palladium nitrate supported on 80 wt % iron nitrate. Typically, 868 mg of Fe(NO<sub>3</sub>)<sub>3</sub>·9H<sub>2</sub>O were added to 20 ml Deionized water in 200 ml beaker and the solution was sonicated for 2 hr. Then, 582 µl of palladium nitrate was added to the solution while stirring process continues for 1 hr. Then, hydrazine hydrate was added by the following ratios (0.1, 0.2, 0.3, 0.4, 0.6, 0.8, 1, 1.6, and 3) ml to the differently prepared samples at room temperature in order to investigate its effect on the catalytic performance of the prepared catalysts.

## 3. RESULTS

From analysis of data obtained using flow reactor under ambient pressure; it was found that increasing the added ratio of hydrazine hydrate to the mixture of palladium nitrate and iron nitrate enhanced the catalytic performance of the catalyst as shown in figure 5. So, the complete conversion was accomplished at lower temperatures until our best temperature at which complete conversion happened was 135 °C as shown in table 1 in the case of 0.4 ml hydrazine hydrate catalyst. While higher temperatures were noticed when using palladium nitrate and iron nitrate alone and also for higher weight ratios of palladium. This may be due to a kind of agglomeration as there is no support used in these two cases which are in agreement with literature.


**Table 1.** Temperatures at which CO conversion reaches 50% (T<sub>50</sub>) and 100% (T<sub>100</sub>) for Pd, Fe<sub>3</sub>O<sub>4</sub>, and the supported catalysts Pd/Fe<sub>3</sub>O<sub>4</sub> using 0.4 ml Hydrazine Hydrate (H.H).

Wt % Pd/Fe <sub>3</sub> O <sub>4</sub>	T <sub>50%</sub> (°C)	T <sub>100%</sub> (°C)
5	194	204
10	180	185
20	125	135
30	130	138
40	142	150
50	162	172
<b>Pd nanoparticles</b>	165	182
<b>Fe<sub>3</sub>O<sub>4</sub> nanoparticles</b>	218	225

The color of the mixture turned to reddish brown and then, it was heated by microwave for (120) s and the black product was finally obtained. The product was then washed with deionized water and the solution was added to centrifuge tubes and centrifugation took place at a rate of 11000 r.p.m for 30 min. The product was washed several times using hot deionized water and then ethanol and finally dried in oven at 80 °C overnight under vacuum.

**2.3. General procedure of Suzuki cross-coupling reactions using Pd/ Fe<sub>3</sub>O<sub>4</sub> catalyst.** 4 mL H<sub>2</sub>O: EtOH (1:1) was used to dissolve (0.24 mmol, 1 eq.), then aryl bromide was added. Aryl boronic acid (0.3 mmol, 1.2 eq.) and potassium carbonate (1.53 mmol, 3 eq.) were also added and hence, 5 g palladium/iron oxide catalyst (Pd-Fe<sub>3</sub>O<sub>4</sub>) was also added and the reaction mixture was then heated using microwave (250 W, 2.45 MHz) at 80 °C for 10 min. The reaction conversion was measured using GC-MS. The catalyst recycling procedure is implemented immediately after the reaction completion where the used solvent was decanted and the catalyst was removed via applying an external magnetic field like a strong magnet. Catalyst was then washed with ethanol several times to remove any residues from the surface of the catalyst. Then, the catalyst is ready for the next run.

**2.4. Characterization of Catalyst.** TEM images were captured via using a Joel JEM-1230 electron microscope. The small angle X-ray diffraction patterns were measured using an X'Pert Philips Diffractometer. The X-ray photoelectron spectroscopy (XPS) spectra were measured on a Thermo Fisher Scientific ESCALAB 250. The prepared catalyst catalytic activity for CO catalytic oxidation was measured using a programmable tube furnace.

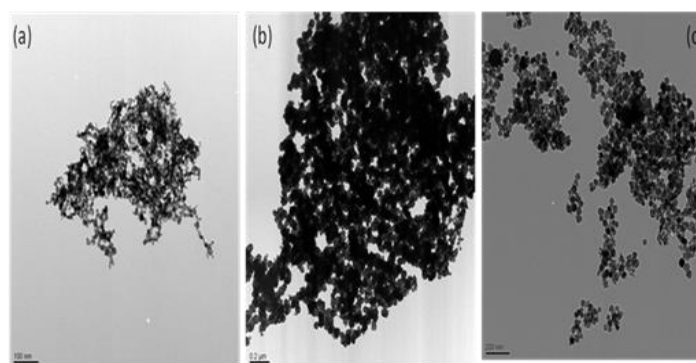

**Figure 2.** TEM of nanoparticles of: (a) Pd, (b) Fe<sub>3</sub>O<sub>4</sub>, (c) Pd/Fe<sub>3</sub>O<sub>4</sub>.

Figure 2- shows TEM image of the Pd nanoparticles prepared by the chemical reduction of Pd(NO<sub>3</sub>)<sub>2</sub> using hydrazine hydrate (HH) under microwave assisted synthesis approach. However, the nanoparticles were of small size range 7-14 nm, but they reveal a significant degree of aggregation due to the absence of a capping agent or support.[9]

Figures 2-b display TEM image of the Fe<sub>3</sub>O<sub>4</sub> nanoparticles. In the case of Fe<sub>3</sub>O<sub>4</sub>, most of the nanoparticles have irregular shapes with diameters between 27-32 nm. Figures 2-c display the TEM images of palladium nanoparticles supported on the Fe<sub>3</sub>O<sub>4</sub> nanoparticles where most of the Pd particles appear to be deposited on the support magnetite nanoplates.


**Table 2.** Effect of Hydrazine Hydrate ration on CO conversion for supported catalysts 20 wt % Pd/Fe<sub>3</sub>O<sub>4</sub>.

No.	H.H (ml)	T <sub>100%</sub> (°C)
1	0.1	246
2	0.2	233
3	0.3	203
4	0.4	135
5	0.6	130
6	0.8	122
7	1	148
8	1.6	165
9	3	195

Table 2 shows the analysis of data obtained using Type F21100 Tube Furnace under ambient pressure; it was found that increasing the added ratio of hydrazine hydrate to the mixture of palladium nitrate and iron nitrate enhanced the catalytic performance and activity of the catalyst. So, the complete conversion was accomplished at lower temperatures until our best temperature at which complete conversion happened was 135 °C as shown in table 1 in case of 0.4 ml hydrazine hydrate catalyst. Increasing hydrazine hydrate could also enhance the complete conversion as it took place at 130, 122 °C for using 0.6 and 0.8 ml hydrazine hydrate respectively.

While higher temperatures were noticed when using palladium nitrate and iron nitrate alone and also for higher ratios of hydrazine hydrate. This may be due to a kind of agglomeration as there is no support used in these two cases which are in agreement with literature.


Figure 3 shows the XRD diffraction patterns of Pd, Fe<sub>3</sub>O<sub>4</sub>, and 20 wt% Pd/Fe<sub>3</sub>O<sub>4</sub> nanoparticles [9]. The typical fcc pattern of Pd crystalline particles was confirmed (JCPDS-46-1043). The characteristic peaks of Fe<sub>3</sub>O<sub>4</sub> nanoparticles were confirmed for the spinal Fe<sub>3</sub>O<sub>4</sub> phase (ICCD-00-003-0863) in addition to the presence of a small percentage of the α-Fe<sub>2</sub>O<sub>3</sub> phase confirmed by the 2θ peaks at 33.3 and 49.6 (JCPDS-33-0664), while for 20 wt% Pd/Fe<sub>3</sub>O<sub>4</sub> nanoparticles, characteristic peaks of Pd and Fe<sub>3</sub>O<sub>4</sub> were confirmed without any indication of the presence of the α-Fe<sub>2</sub>O<sub>3</sub> phase. These results are in good agreement with other reported data [34-37].

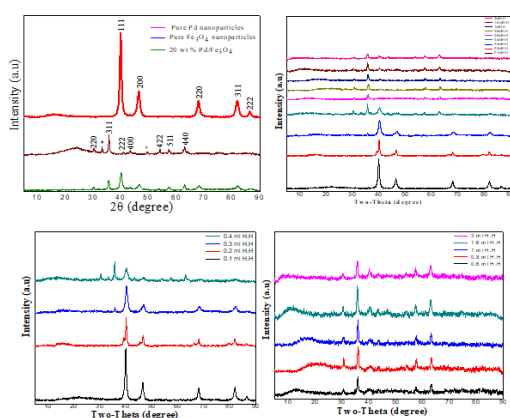


**Figure 3.** (a) XRD patterns of Pd, Fe<sub>3</sub>O<sub>4</sub>, and 20 wt% Pd/Fe<sub>3</sub>O<sub>4</sub> prepared using 0.4 ml hydrazine hydrate. (b, c, d) XRD patterns of 20 wt% Pd/Fe<sub>3</sub>O<sub>4</sub> prepared using different hydrazine hydrate ratios. (\* is due to Fe<sub>2</sub>O<sub>3</sub>).

The characterization of the surface composition of the supported nanocatalysts, was carried out via using XPS measurements as shown in Figures 4 (a) and 4 (b). The presence of Fe(III) was confirmed through peaks at 724.2 eV and 710.5 eV corresponding to the binding energies of the 2p<sup>1/2</sup> and 2p<sup>3/2</sup> electrons, respectively [35-37].

Similarly, the characteristic binding energies of 334.8 eV and 340.1 eV confirm the presence of Pd<sup>0</sup> and Pd<sup>2+</sup> (due to the presence of PdO)[6, 9, 10, 13, 15, 18, 35-37].

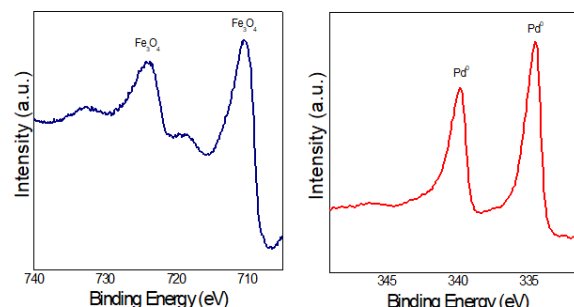

**Figure 4.** XPS binding energy of (a) Fe 2p region (b) Pd 3d region for Pd/Fe<sub>3</sub>O<sub>4</sub>.

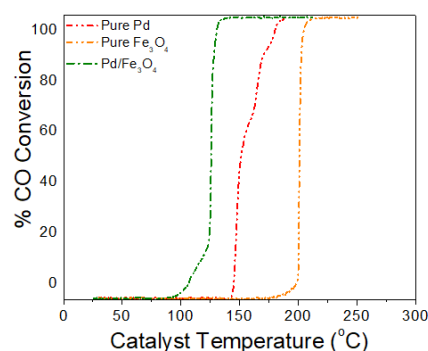

**Figure 5.** CO catalytic oxidation by 20 wt % Pd/Fe<sub>3</sub>O<sub>4</sub> with pure Pd and Fe<sub>3</sub>O<sub>4</sub> nanoparticles.

Figure 5 compares the catalytic activity of oxidation of carbon monoxide over pure Fe<sub>3</sub>O<sub>4</sub>, pure Pd nanoparticles, and 20 wt% Pd/Fe<sub>3</sub>O<sub>4</sub>. The catalytic activities of pure Pd and pure support nanoparticles were measured as a standard in order to compare with the supported catalysts.

It was found that both the pure Fe<sub>3</sub>O<sub>4</sub> and pure Pd nanoparticles reveal poor activities with 100% conversion temperatures of 225 °C and 182 °C, respectively as discussed before in table 1. This is mostly due to the aggregation of the Pd and magnetite nanoparticles due to the absence of using any kind of supports. However, catalysts containing 20 wt % Pd show excellent catalytic behavior with 100% conversion temperatures of 125 °C compared to the pure Pd and pure magnetite nanoparticle catalyst indicating the well-established significant role of the support in dispersing the catalyst nanoparticles and decreasing their tendency for aggregation and sintering. Therefore, it appears that the 20 wt% Pd/Fe<sub>3</sub>O<sub>4</sub> catalyst provides reasonable optimization between the adsorption of the CO and O<sub>2</sub> molecules on the Pd-Fe<sub>3</sub>O<sub>4</sub> interfaces to allow efficient oxidation of CO which is in good agreement with other reported data for similar catalytic systems[38-46].

#### 4. CONCLUSIONS

In conclusion, a facile one-step approach has been adopted for the synthesis of Pd nanoparticle catalysts supported on Fe<sub>3</sub>O<sub>4</sub> nanoparticles via microwave assisted synthesis. Moreover, the recovery and the recycling process of the catalyst could be implemented up to five times with high catalytic activity near 100% thus providing high economic viability. It can be easily concluded from characterization that palladium nanoparticles are uniformly dispersed onto the surface of magnetite nanosheets.

This easy and efficient recycling process of the catalyst is simply due to the magnetic properties of magnetite, thus lead to achieving high yields over different substrates for Suzuki cross coupling reactions which is one of the main reactions used in pharmaceutical applications.

The important advantage of this method over other methods besides the fast synthetic route is the reproducibility of the final product in order to avoid other issues raised by other techniques.

#### 5. REFERENCES

1. Chen, S.T.; Si, R.; Taylor, E.; Janzen, J.; Chen, J. Synthesis of Pd/Fe<sub>3</sub>O<sub>4</sub> Hybrid Nanocatalysts with Controllable Interface and Enhanced Catalytic Activities for CO Oxidation. *Journal of Physical Chemistry C* **2012**, *116*, 12969-12976, <https://doi.org/10.1021/jp3036204>.
2. Radwan, N.R.E.; El-Shall, M.S.; Hassan, H.M.A. Synthesis and characterization of nanoparticle Co<sub>3</sub>O<sub>4</sub>, CuO and NiO catalysts prepared by physical and chemical methods to minimize air pollution. *Applied Catalysis A: General* **2007**, *331*, 8-18, <https://doi.org/10.1016/j.apcata.2007.07.005>.
3. Wang, H.L.; Casalongue, H.S.; Liang, Y.; Dai, H. Ni(OH)<sub>2</sub> Nanoplates Grown on Graphene as Advanced Electrochemical Pseudocapacitor Materials. *Journal of the American Chemical Society* **2010**, *132*, 7472-7477, <https://doi.org/10.1021/ja102267j>.
4. Wang, W.W.; Zhu, Y.J.; Ruan, M.L. Microwave-assisted synthesis and magnetic property of magnetite and hematite nanoparticles. *Journal of Nanoparticle Research* **2007**, *9*, 419-426, <https://doi.org/10.1007/s11051-005-9051-8>.
5. Elazab, H.; Sadek, M.A.; El-Idreesy, T. Microwave-assisted synthesis of Pd nanoparticles supported on FeO, CoO, and Ni(OH)<sub>2</sub> nanoplates and catalysis application for CO oxidation. *Journal of Nanoparticle Research* **2014**, *16*, 1-11, <https://doi.org/10.1177/0263617418771777>.
6. Mankarious, R.A.; Radwan, M.A.; Shazly, M.; Elazab, H.A.; Bulletproof vests/shields prepared from composite material based on strong polyamide fibers and epoxy resin. *Journal of Engineering and Applied Sciences* **2017**, *12*, 2697-2701.
7. Mohsen, W.; Sadek, M.A.; Elazab, H.A. Green synthesis of copper oxide nanoparticles in aqueous medium as a potential efficient catalyst for catalysis applications. *International Journal of Applied Engineering Research* **2017**, *12*, 14927-14930, <http://dx.doi.org/10.13005/msri/150311>.
8. Mostafa, A.R.; Omar, H.A.S.; Hany, A.E. Preparation of Hydrogel Based on Acryl Amide and Investigation of Different Factors Affecting Rate and Amount of Absorbed Water. *Agricultural Sciences* **2017**, *8*, 11, <https://doi.org/10.4236/as.2017.82011>.
9. Radwan, M.A.; Naem, M.M.; Sadek, M.A.; Elazab, H.A. Mechanical characteristics for different composite materials based on commercial epoxy resins and different fillers. *Journal of Engineering and Applied Sciences* **2017**, *12*, 1179-1185.

Furthermore, the current research results reveal that the Pd/Fe<sub>3</sub>O<sub>4</sub> catalyst has particularly high activity for CO oxidation as a result of the strong interaction between the Pd nanoparticles and the Fe<sub>3</sub>O<sub>4</sub> nanoparticles. It was found that the prepared catalyst containing 20 wt % Pd reveal excellent catalytic performance with 100% conversion temperatures of 125 °C compared to the pure Pd and pure magnetite nanoparticle catalyst indicating the well-established significant role of the support in dispersing the catalyst nanoparticles and decreasing their tendency for aggregation and sintering. Optimizations of the particle size, chemical composition, and shape of those catalysts could help to design more efficient nanocatalysts with higher catalytic activity. We are currently exploring other effects of microwave heating duration; different supports including carbon based structures as well as the effect of particle size, and shape of the supported metal nanoparticle catalysts.

10. Andrade, A.L.; Pereira, M.C.; Domingues, R.Z.; Souza, D.M.; Fabris, D.J. Catalytic Effect of Magnetic Nanoparticles Over the H<sub>2</sub>O<sub>2</sub> Decomposition Reaction. *Journal of Nanoscience and Nanotechnology* **2009**, *9*, 3695-3699.
11. Kustov, A.L.; Frey, A.M.; Larsen, K.E.; Johannessen, T.; Nørskov, J.K.; Christensen, C.H. CO methanation over supported bimetallic Ni-Fe catalysts: From computational studies towards catalyst optimization. *Applied Catalysis a-General* **2007**, *320*, 98-104, <https://doi.org/10.1016/j.apcata.2006.12.017>.
12. Lohitharn, N.; Goodwin, J.G. Impact of Cr, Mn and Zr addition on Fe Fischer-Tropsch synthesis catalysis: Investigation at the active site level using SSITKA. *Journal of Catalysis* **2008**, *257*, 142-151, <https://doi.org/10.1016/j.jcat.2008.04.015>.
13. Moreau, F.; Bond, G.C. CO oxidation activity of gold catalysts supported on various oxides and their improvement by inclusion of an iron component. *Catalysis Today* **2006**, *114*, 362-368, <https://doi.org/10.1016/j.cattod.2006.02.074>.
14. Sarkari, M.; Fazlollahi, F.; Atashi, H.; Mirzaei, A.A.; Hosseinpour, V. Fischer-Tropsch synthesis: Development of kinetic expression for a sol-gel Fe-Ni/Al<sub>2</sub>O<sub>3</sub> catalyst. *Fuel Processing Technology* **2012**, *97*, 130-139, <https://doi.org/10.1016/j.fuproc.2012.01.008>.
15. Elazab, H.; Moussa, S.; Siamaki, A.R.; Gupton, F.B.; El-Shall, M.S. The Effect of Graphene on Catalytic Performance of Palladium Nanoparticles Decorated with FeO, CoO, and Ni(OH)<sub>2</sub>: Potential Efficient Catalysts Used for Suzuki Cross-Coupling. *Catalysis Letters* **2017**, *147*, 1510-1522, <https://doi.org/10.1007/s10562-017-1990-z>.
16. Elazab, H.A.; Moussa, S.; Brinkley, K.W.; Gupton, B.F.; El-Shall, M.S. The continuous synthesis of Pd supported on Fe<sub>3</sub>O<sub>4</sub> nanoparticles: A highly effective and magnetic catalyst for CO oxidation. *Green Processing and Synthesis* **2007**, *6*, 413-424, <https://doi.org/10.1515/gps-2016-0168>.
17. Elazab, H.A.; Sadek, M.A.; El-Idreesy, T.T. Microwave-assisted synthesis of palladium nanoparticles supported on copper oxide in aqueous medium as an efficient catalyst for Suzuki cross-coupling reaction. *Adsorption Science & Technology* **2018**, <https://doi.org/10.1177/0263617418771777>.
18. Elazab, H.A.; Siamaki, A.R.; Moussa, S.; Gupton, F.B.; El-Shall, M.S. Highly efficient and magnetically recyclable graphene-supported Pd/Fe<sub>3</sub>O<sub>4</sub> nanoparticle catalysts for Suzuki

- and Heck cross-coupling reactions. *Applied Catalysis A: General* **2015**, *491*, 58-69, <https://doi.org/10.1016/j.apcata.2014.11.033>.
19. Hirvi, J.T.; Kinnunen, T.J.J.; Suvanto, M.; Pakkanen, T.A.; J.K., Nørskov. CO oxidation on PdO surfaces, *Journal of Chemical Physics* **2010**, *133*, <https://doi.org/10.1063/1.3464481>.
20. Iglesias-Juez, A.; Kubacka, A.; Gernandez-Garcia, M.; Di Michiel, M.; Newton, M.A. Nanoparticulate Pd Supported Catalysts: Size-Dependent Formation of Pd(I)/Pd(0) and Their Role in CO Elimination. *Journal of the American Chemical Society* **2011**, *133*, 484-4489, <https://doi.org/10.1021/ja110320y>.
21. Ivanova, A.S.; Slavinskayaa, E.M.; Gulyaeva, R.V.; Zaikovskii, V.I.; Stonkusb, O.A.; Danilovaa, I.G.; Plyasovaa, L.M.; Polukhinaa, I.A.; Boroninab, A.I. Metal-support interactions in Pt/Al<sub>2</sub>O<sub>3</sub> and Pd/Al<sub>2</sub>O<sub>3</sub> catalysts for CO oxidation **2010**. *Applied Catalysis B-Environmental*, *97*, 57-71, <https://doi.org/10.1016/j.apcatb.2010.03.024>.
22. Kim, H.Y.; Henkelman, G. CO Oxidation at the Interface between Doped CeO<sub>2</sub> and Supported Au Nanoclusters. *Journal of Physical Chemistry Letters* **2012**, *3*, 2194-2199, <https://doi.org/10.1021/jz300631f>
23. Chattopadhyay, K.; Dey, R.; Ranu, B.C. Shape-dependent catalytic activity of copper oxide-supported Pd(0) nanoparticles for Suzuki and cyanation reactions. *Tetrahedron Letters: International Organ for the Rapid Publication of Preliminary Communications in Organic Chemistry* **2009**, *50*, 3164-3167, <https://doi.org/10.1016/j.tetlet.2009.01.027>.
24. Hoseini, S.J.; Agahi, B.H.; Fard, S.Z.; Fath, R.H.; Bahrami, M. Modification of palladium-copper thin film by reduced graphene oxide or platinum as catalyst for Suzuki-Miyaura reactions. *Applied Organometallic Chemistry* **2017**, *31*, <https://doi.org/10.1002/aoc.3607>.
25. Hosseini-Sarvari, M.; Razmi, Z. Palladium Supported on Zinc Oxide Nanoparticles as Efficient Heterogeneous Catalyst for Suzuki Miyaura and Hiyama Reactions under Normal Laboratory Conditions. *Helvetica Chimica Acta* **2015**, *98*, 805-818, <https://doi.org/10.1002/hlca.201400331>.
26. Nasrollahzadeh, M.; Ehsani, A.; Jaleh, B. Preparation of carbon supported CuPd nanoparticles as novel heterogeneous catalysts for the reduction of nitroarenes and the phosphine-free Suzuki Miyaura coupling reaction. *New Journal of Chemistry* **2015**, *39*, 1148-1153, <https://doi.org/10.1039/C4NJ01788A>.
27. Nasrollahzadeh, M.; Sajadi, M.; Rostami-Vartooni, A.; Azarian, A. Palladium nanoparticles supported on copper oxide as an efficient and recyclable catalyst for carbon(sp<sup>2</sup>) carbon(sp<sup>2</sup>) cross-coupling reaction. *Materials Research Bulletin* **2013**, *68*, 150-154, <https://doi.org/10.1016/j.materresbull.2015.03.051>.
28. Mandali, P.K.; Chand, D.K. Palladium nanoparticles catalyzed Suzuki cross-coupling reactions in ambient conditions. *Catalysis Communications* **2016**, *31*, 16-20, <https://doi.org/10.1016/j.catcom.2012.10.020>.
29. Wang, Y.; Wen, Y.; Zhang, H.; Cao, G.; Sun, W.; Cao, J.; CuO Nanorods-Decorated Reduced Graphene Oxide Nanocatalysts for Catalytic Oxidation of CO. *Catalysts* **2016**, *6*, 214, <https://doi.org/10.3390/catal6120214>
30. Igarashi, H.; Uchida, H.; Watanabe, M. Mordenite-supported noble metal catalysts for selective oxidation of carbon monoxide in a reformed gas. *Chemistry Letters* **2000**, *11*, 1262-1263, <https://doi.org/10.1246/cl.2000.1262>.
31. Liu, W.H.; Fleming, S.; Lairson, B.M. Reduced intergranular magnetic coupling in Pd/Co multilayers. *Journal of Applied Physics* **1996**, *79*, 3651-3655, <https://doi.org/10.1063/1.361193>.
32. Luo, J.Y.; Meng, M.; Li, X.; Li, G.X.; Zha, Y.Q.; Hu, T.D.; Xie, Y.N.; Zhang, J. Mesoporous Co(3)O(4)-CeO(2) and Pd/Co(3)O(4)-CeO(2) catalysts: Synthesis, characterization and mechanistic study of their catalytic properties for low-temperature CO oxidation. *Journal of Catalysis* **2008**, *254*, 310-324, <https://doi.org/10.1016/j.jcat.2008.01.007>.
33. Pavlova, S.N.; Sadykov, V.A.; Bulgakov, N.N.; Bredikhin, M.N. The influence of support on the low-temperature activity of Pd in the reaction of CO oxidation. Kinetics and mechanism of the reaction. *Journal of Catalysis* **1996**, *161*, 517-523, <https://doi.org/10.1006/jcat.1996.0213>.
34. Diyarbakir, S.M.; Can, H.; Metin, O. Reduced Graphene Oxide-Supported CuPd Alloy Nanoparticles as Efficient Catalysts for the Sonogashira Cross-Coupling Reactions. *Acs Applied Materials & Interfaces* **2015**, *7*, 3199-3206, <https://doi.org/10.1021/am507764u>.
35. Feng, Y.S.; Ma, J.J.; Kang, Y.M.; Xu, H.J. PdCu nanoparticles supported on graphene: an efficient and recyclable catalyst for reduction of nitroarenes. *Tetrahedron* **2014**, *70*, 6100-6105, <https://doi.org/10.1016/j.tet.2014.04.034>.
36. Liu, Y.; Ma, H.; Gao, J.; Wu, D.; Ren, X.; Yan, T.; Pang, X.; Wei, Q. Ultrasensitive electrochemical immunosensor for SCCA detection based on ternary Pt/PdCu nanocube anchored on three-dimensional graphene framework for signal amplification. *Biosensors & Bioelectronics* **2016**, *79*, 71-78, <https://doi.org/10.1016/j.bios.2015.12.013>.
37. Shafaei, D.A.; Saravani, H.; Noroozifar, M. Novel fabrication of PdCu nanostructures decorated on graphene as excellent electrocatalyst toward ethanol oxidation. *International Journal of Hydrogen Energy* **2017**, *42*, 15149-15159, <https://doi.org/10.1016/j.ijhydene.2017.04.280>.
38. Elazab, H.A. Investigation of Microwave-assisted Synthesis of Palladium Nanoparticles Supported on Fe<sub>3</sub>O<sub>4</sub> as an Efficient Recyclable Magnetic Catalysts for Suzuki Cross – Coupling. *The Canadian Journal of Chemical Engineering* **2018**, *96*, 250-261, <https://doi.org/10.1002/cjce.23402>.
39. Elazab, H.A. Laser Vaporization and Controlled Condensation (LVCC) of Graphene supported Pd/Fe<sub>3</sub>O<sub>4</sub> Nanoparticles as an Efficient Magnetic Catalysts for Suzuki Cross – Coupling. *Biointerface Research in Applied Chemistry* **2018**, *8*, 3314 – 3318.
40. Elazab, H.A. The catalytic Activity of Copper Oxide Nanoparticles towards Carbon Monoxide Oxidation Catalysis: Microwave – Assisted Synthesis Approach. *Biointerface Research in Applied Chemistry* **2018**, *8*, 3278 – 3281.
41. Radwan, M.A.; Al-Sweasy, O.; Sadek, M.A.; Elazab, H.A. Investigating the Agricultural Applications of Acryl Amide based Hydrogel. *International Journal of Engineering and Technology(UAE)* **2018**, *7*, 168-171.
42. Zakaria, F.; Radwan, M.A.; Sadek, M.A.; Elazab, H.A. Insulating material based on shredded used tires and inexpensive polymers for different roofs. *International Journal of Engineering and Technology(UAE)* **2018**, *7*, 4, 1983-1988.
43. Nasser, R.; Radwan, M.A.; Sadek, M.A.; Elazab, H.A. Preparation of insulating material based on rice straw and inexpensive polymers for different roofs. *International Journal of Engineering and Technology(UAE)* **2018**, *7*, 1989-1994.
44. Ghobashy, M.; Gadallah, M.; El-Idreesy, T.T.; Sadek, M.A.; Elazab, H.A. Kinetic Study of Hydrolysis of Ethyl Acetate using Caustic Soda **2018**. *International Journal of Engineering and Technology(UAE)* **2018**, *7*, 1995-1999, <http://dx.doi.org/10.14419/ijet.v7i4.14083>.

45. Samir, N.S.; Radwan, M.A.; Sadek, M.A.; Elazab, H.A. Preparation and Characterization of Bullet-Proof Vests Based on Polyamide Fibers. *International Journal of Engineering and Technology (UAE)* **2018**, *7*, 1290-1294, <http://dx.doi.org/10.14419/ijet.v7i3.13175>.

46. Ashraf, B.; Radwan, M.A.; Sadek, M.A.; Elazab, H.A. Preparation and Characterization of Decorative and Heat Insulating Floor Tiles for Buildings Roofs. *International Journal of Engineering and Technology (UAE)* **2018**, *7*, 1295-1298, <http://dx.doi.org/10.14419/ijet.v7i3.13177>.

## 6. ACKNOWLEDGEMENTS

We gratefully express our deep gratitude to The British University in Egypt (BUE) for supporting this work through Young Investigator Research Grant (YIRG) awarded to Dr. Hany A. Elazab.



© 2019 by the authors. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).